



中国认可
国际互认
检测
TESTING
CNAS L2249

REPORT No.17-1081



TEST REPORT

PRODUCT PLYWOOD

COMPANY XUZHOU HUAYU WOOD INDUSTRY CO., LTD.

CLASSIFYING ENTRUSTED TESTING



国家林业局人造板及其制品质量检验检测中心(南京)

南京林业大学木材及其制品测试中心

WOOD PRODUCTS QUALITY TEST & INSPECTION CENTER
OF STATE FORESTRY ADMINISTRATION (NANJING)

ADD: No.159 Longpan Road, Nanjing Forestry University, Jiangsu Province, China

中国江苏省南京市龙蟠路 159 号 南京林业大学内

TEL: 025-85427522/85485181 FAX: 025-85427522 PC: 210037

OF STATE FORESTRY ADMINISTRATION (NANJING)

TESTING REPORT

No.17-1081

4 PAGES No.1

Inspected unit	XUZHOU HUAYU WOOD INDUSTRY CO., LTD.		
Production unit	XUZHOU HUAYU WOOD INDUSTRY CO., LTD.		
Product name	Plywood	Trademark	
Product size	Thickness: 14mm	Testing classification	Entrusted testing
Grade	Acceptable part	Standard	EN314-1, EN314-2, EN 310 EN322, EN717-2, EN323
Batch No./ Production date	// 2017-08-31	Sample size	mm: 600×600×14 4pcs
Bonding class	/	Wood species	Poplar
Testing item	Moisture content, Density, Bonding quality, Modulus of elasticity in bending, Bending strength, formaldehyde release		
Conclusion	<p>Required by XUZHOU HUAYU WOOD INDUSTRY CO., LTD. according to the standard EN322, EN323, EN314-1, EN314-2, EN 310 and EN717-2, Wood Products Quality & Inspection Center of State Forestry Administration (Nanjing) tests its sending the plywood samples' Mechanical properties (Moisture content, Density, Bonding quality, Modulus of elasticity in bending, Bending strength) and formaldehyde release.</p> <p>Test values see in Page 2、Page3 and Page4</p> <p style="text-align: right;">Testing unit(stamp) Issuing date: October 2017</p>		
Remarks	<p>1. The production unit's name and trademark of the product are supplied by the inspected unit.</p> <p>2. This report is only responsible for sending samples.</p> <p>3. Bonding quality' details of pretreatments EN314-1 5.1.1: Immersion for 24 hours in water at (20±3)°C. EN314-13 5.1.4: Immersion for (72±1) hours in boiling water, followed by cooling in water at(20±3)°C for at least 1 hour to decrease temperature of test pieces to 20°C.</p>		

Approved by: 苏门德 Reviewed by: 梁金宇 Tested by: 曹新高

WOOD PRODUCTS QUALITY TEST & INSPECTION CENTER
OF STATE FORESTRY ADMINISTRATION (NANJING)

TESTING REPORT

No.17-1081

4 PAGES No.2

Inspected unit	XUZHOU HUAYU WOOD INDUSTRY CO., LTD.			
Product name	Plywood	Sampling method	Sending	
Product size	Thickness: 14mm	Standard	EN314-1, EN314-2, EN310 EN322, EN717-2, EN 323	
Testing date	September 25, 2017 TO October 12, 2017			
Testing item		Unit	Standard used	Tested value
Bonding quality (glueline 1)	Mean shear strength(f_v)	N/mm ²	EN 314 (pretreatments by EN314-1 5.1.1)	1.14
	The standard deviation	—		0.08
	Mean apparent cohesive wood failure (W)	%		84
Bonding quality (glueline 2)	Mean shear strength(f_v)	N/mm ²	EN 314 (pretreatments by EN314-1 5.1.1)	1.20
	The standard deviation	—		0.16
	Mean apparent cohesive wood failure (W)	%		74
Bonding quality (glueline 3)	Mean shear strength(f_v)	N/mm ²	EN 314 (pretreatments by EN314-1 5.1.1)	1.23
	The standard deviation	—		0.07
	Mean apparent cohesive wood failure (W)	%		63
Bonding quality (glueline 4)	Mean shear strength(f_v)	N/mm ²	EN 314 (pretreatments by EN314-1 5.1.1)	1.22
	The standard deviation	—		0.25
	Mean apparent cohesive wood failure (W)	%		100



WOOD PRODUCTS QUALITY TEST & INSPECTION CENTER

OF STATE FORESTRY ADMINISTRATION (NANJING)

TESTING REPORT

No.17-1081

4 PAGES No.3

Inspected unit		XUZHOU HUAYU WOOD INDUSTRY CO., LTD.		
Product name		Plywood	Sampling method	Sending
Product size		Thickness: 14mm	Standard	EN314-1,EN314-2,EN310 EN322, EN717-2,EN 323
Testing date		September 25, 2017 TO October 12, 2017		
Testing item		Unit	Standard used	Tested value
Bonding quality (glueline 1)	Mean shear strength(f_v)	N/mm ²	EN 314 (pretreatments by EN314-1 5.1.4)	1.04
	The standard deviation	—		0.09
	Mean apparent cohesive wood failure (W)	%		77
Bonding quality (glueline 2)	Mean shear strength(f_v)	N/mm ²	EN 314 (pretreatments by EN314-1 5.1.4)	1.08
	The standard deviation	—		0.19
	Mean apparent cohesive wood failure (W)	%		41
Bonding quality (glueline 3)	Mean shear strength(f_v)	N/mm ²	EN 314 (pretreatments by EN314-1 5.1.4)	1.02
	The standard deviation	—		0.10
	Mean apparent cohesive wood failure (W)	%		55
Bonding quality (glueline 4)	Mean shear strength(f_v)	N/mm ²	EN 314 (pretreatments by EN314-1 5.1.4)	1.05
	The standard deviation	—		0.10
	Mean apparent cohesive wood failure (W)	%		53



WOOD PRODUCTS QUALITY TEST& INSPECTION CENTER

OF STATE FORESTRY ADMINISTRATION (NANJING)

TESTING REPORT

No.17-1081

4 PAGES No.4

Inspected unit		XUZHOU HUAYU WOOD INDUSTRY CO., LTD.			
Product name		Plywood	Sampling method	Sending	
Product size		Thickness: 14mm	Standard	EN314-1,EN314-2,EN310	
Testing date		September 25, 2017 TO October 12, 2017		EN322, EN717-2,EN 323	
Testing item		Unit	Standard used	Tested value	
Bending strength	Longitudinal grain	N/mm ²	EN 310	Panel average	50.2
				Standard deviation	8.1
	Cross grain	N/mm ²		Panel average	43.2
				Standard deviation	4.0
Moisture content		%	EN322	Average: 7.3	
Density		kg/m ³	EN323	Average: 548	
Modulus of elasticity in bending	Longitudinal grain	N/mm ²	EN 310	Panel average	5915
				Standard deviation	335.0
	Cross grain	N/mm ²		Panel average	4108
				Standard deviation	213.7
Formaldehyde release		mg/m ² h	EN717-2	Average: 0.88	
remarks	Moisture content (specimen dimension:50mm×50mm×14mm; number: 6) Density(specimen dimension:50mm×50mm×14mm; number: 6) Bending strength(specimen dimension: 330mm×50mm×14mm; number: 6 with Longitudinal grain fibers and 6 with Cross grain fibers) Bonding quality(specimen dimension: 100mm×25mm×14mm; 10 test pieces per glue line) Modulus of elasticity in bending(specimen dimension: 330mm×50mm×14mm; number: 6 with Longitudinal grain fibers and 6 with Cross grain fibers) Formaldehyde release (specimen dimension:400mm×50mm×14mm; number: 2)				



TEST REPORT

CheckCode: 211822
Report No. : C201711139686-44E

Applicant: Xuzhou Huayu Wood Co., Ltd.
Address: San Bao Zhen Sheng Yang Industrial Park, Tongshan County, Xuzhou City, Jiangsu Province

Report on the submitted sample(s) said to be:

Name: Plywood
Material No.: ----
Product Series: ----
Supplier Code: ----
Manufacturer: ----

Date of Receipt: Apr.8, 2018 **Test period:** Apr.8, 2018 – Apr.19, 2018

Test Request: Please refer to following page(s).

Test Result: Please refer to following page(s).

Conclusion: Please refer to following page(s).



Edited by Zoe Tang Reviewed by Lank Wang Approved by Yoland Yan



Seal of: GUANGZHOU GRG METROLOGY & TEST CO., LTD.

Issue date: Apr 19, 2018

This test report is responsible for the tested samples only. Without permission of the test center this test report is not permitted to be duplicated in extracts. The test report is invalid without the specialized stamp of GUANGZHOU GRG METROLOGY & TEST CO., LTD. The test report is invalid if altered. Objections to the test report must be submitted to GUANGZHOU GRG METROLOGY & TEST CO., LTD. within 15 days.

GUANGZHOU GRG METROLOGY & TEST CO., LTD.

Address: 163 Pingyun Road West of Huangpu Avenue Tianhe District Guangzhou City, 510656, P. R. China
Tel: +86-020-66664900 FAX: +86-020-38698685 <http://www.grgtest.com>



TEST REPORT

CheckCode: 211822
Report No. : C201711139686-44E

No.	Test Item	Client and Regulation Requirements	Conclusion
6	Formaldehyde	Limit< 0.05ppm	Comply

Sample description:

1. Light brown plywood with black coating

Test Result(s):

Formaldehyde

Test Method: With reference to ASTM D 5582-2014, analysis with UV-Vis spectrophotometer.

Test Item	Result	Unit	MDL
	1		
Formaldehyde (HCHO)	N.D.	µg/mL	0.01

Remark: 1) µg/mL = ppm
2) "N.D." = Not Detected (Below Method Detection Limit)
3) MDL = method detection limit

GUANGZHOU GRG METROLOGY & TEST CO., LTD.


Address: 163 Pingyun Road West of Huangpu Avenue Tianhe District Guangzhou City, 510656, P. R. China
Tel: +86-020-66664900 FAX: +86-020-38698685 <http://www.grgtest.com>



TEST REPORT

CheckCode: 211822
Report No. : C201711139686-44E

Photo of Sample

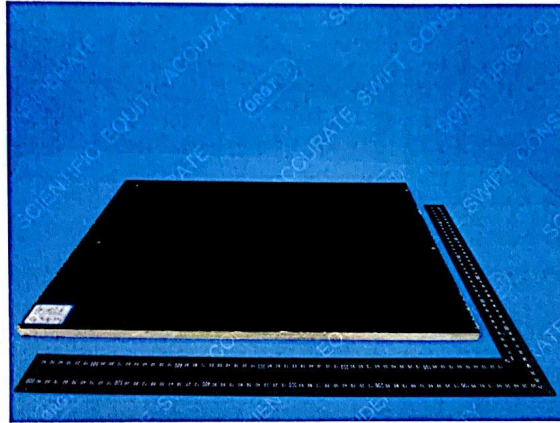

-----End of Report-----

GUANGZHOU GRG METROLOGY & TEST CO., LTD.

Address: 163 Pingyun Road West of Huangpu Avenue Tianhe District Guangzhou City, 510656, P. R. China
Tel: +86-020-66664900 FAX: +86-020-38698685 <http://www.grgtest.com>